



OPTIMIZATION OF RAP AND SASOBIT FOR PERMANENT DEFORMATION AND MOISTURE DAMAGE OF ASPHALT MIXES

Fazal Haq
Postgraduate Student & Research Assistant,
National Institute of Transportation,
SCEE, NUST
Main Campus, Islamabad, Pakistan

Arshad Hussain
Assistant Professor,
National Institute of Transportation,
SCEE, NUST
Main Campus, Islamabad, Pakistan

Muhammad Bilal khurshid
Associate Professor,
National Institute of Transportation,
SCEE, NUST
Main Campus, Islamabad Pakistan

Abstract— Recycling of Reclaimed Asphalt Pavement provide us with the need to save valuable aggregate and with the help of which the use of expensive asphalt binder will be reduced as well. In this study we have considered one WMA additive (Sasobit). The rut resistances of mixes were improved by adding either RAP or Sasobit or both as compared to control asphalt mixes. But for lower percentages of RAP i.e. up to 15%, highest rut resistance was observed at 2% Sasobit addition, but for higher percentages of RAP highest rut resistance was observed at 3% Sasobit addition. On the other hand, increasing RAP and Sasobit content increased the moisture susceptibility of mixes, so best recommended combination is to use 30-40% RAP in addition of 3% Sasobit as far as permanent deformation and moisture susceptibility criteria are concerned.

Keywords— HMA, WMA, Sasobit, Permanent Deformation, Rutting, Moisture Damage.

I. INTRODUCTION

The increasing plea on our thoroughfares over the past couple of decade's results in a decrease of budgetary funds and to offer a cost effective, safe and efficient system of roads has steered to intense growth in the need to rehabilitate our present roadways.

Moreover, historical data revealed that the RAP mixes could have similar performance as virgin HMA

mixtures, when accurately designed and constructed [1]. Many innovative products and procedures are available having proficiency of dropping the mixing temperature of HMA without negotiating the concert and harmony of the pavement. About 40% reductions in mixing and compaction temperatures are possible by using these products [2]. With the lower operating temperature another aided benefit is that it will reduce the oxidative hardening of the binder and this will help in increased performance of the pavement, such as averting the mix from being tender when placed, reduced block cracking and thermal cracking [2].

Sasobit is a long-chain hydrocarbon (aliphatic poly-methylene), fine crystalline, formed from the gasification of natural gas or coal feed stocks by the Fischer-Tropsch (FT) procedure (in which partial oxidation of methane to carbon monoxide (CO) takes place, and later on reacting with hydrogen (H) manufacturing a combination of hydrocarbons under catalytic conditions with molecular chain lengths of plus C5 to C100 carbon atoms).

Sasobit is an "asphalt flow improver" and is perfectly soluble in bitumen at a temperature higher than 120°C, because of its melting temperature of about 102°C and it also forms a crystalline grid structure in the binder at a temperature below its melting point that leads to additional permanency [3].



The range for Sasobit use as endorsed by Sasol is from 0.8% to 3% by mass of binder. In marketable applications in Asia, Europe, the United States and South Africa Sasobit has been mixed straight with aggregate mix as melted liquid through a dosing meter or solid prills (small pellets). Marshall tests executed on blends prepared in this way signposted no variance in flow or stability values as associated to premixing with the binder [4]. For the purpose of comparing with conventional HMA technology, we need to carry out an inclusive laboratory and field examination to explore permanent deformation and moisture damage of WMA technology. The temperature regimes at which WMA are produced will help to distinguish it from other asphalt mixtures and then by comparing the strength and durability of final product [5]. There are extensive conclusions for WMA additives. Info obtained from industrialists and materials traders specify that, there is possibility to reduce CO₂ emissions and energy consumption to about 30% as compared to standard HMA [6]. A positive influence on pavement performance may be demonstrated by these technologies, as they allow reduced HMA mixing and compaction temperature [7]. Using Sasobit there is an opportunity of dropping the production temperatures by 18–54°C [8] [9]. By lowering the production temperature, we can extend the paving season as the capability to perform late/early-season paving will be enhanced. This is due to the asphalt mix preparation occurs at a reduced temperature, will not cool as quickly, thus allow a longer production time period [10].

Rutting is the accumulation of small amount of irrecoverable strain due to applied load on the pavement, also known as permanent deformation [10]. Rutting has become the major mode of flexible pavement failure because of increase in truck pressure in the last decades. Rutting is principally caused by the accumulation of permanent deformation in different layers and in different portion of layers in the pavement structure. There are two types of rutting: Instability rutting, which is caused by weak asphalt layers and structural rutting, which is caused by weak subgrade [12]. It has been revealed that for the larger part of the lifetime of the roadway, shear deformation is considered to be the primary mechanism of rutting [11]. Using some of WMA products along with high percentage of RAP may badly affect the rutting potential, because of reduced stiffness because of lower production temperature [13]. Physical behavior of HMA changes when RAP is added. RAP binder's increased stiffness is thought to be the cause of higher modulus of HMA. In the same way it also disturbs the mixture's low temperature cracking as well as its fatigue behavior [1].

Moisture damage can be defined as the loss of durability and strength of asphalt mix affected by moisture. Moisture damage is the result of interaction of moisture with the adhesion between asphalt aggregate and binder, and thus during cyclic loading it become more susceptible to moisture. It means that asphalt mixture can result moisture damage because of reduced bond strength with in the fine aggregate and the asphalt binder [11]. Moisture present in air voids

adversely affect the durability and strength of asphalt mixes and causes moisture damage. Moisture damage can occur in two different types: cohesive failure and adhesive failure. Cohesive failure is the strength reduction of the binder due to moisture damage, while Adhesive failure is in between the aggregate and binder [14]. Conventional measure of moisture susceptibility can be reinforced by the consideration of contact angle measurements and dynamic modulus results, which were proposed recently to be promising alternatives to assess moisture susceptibility of asphalt mixes [15]. According to Washington State Department of Transportation (2009) [16], Indirect tensile strength test is a very common and easy performance test conducted in the paving industry, which aid in measuring the asphalt mix susceptibility to moisture. In Indirect tensile strength testing, we test conditioned and unconditioned samples, which provide a consistent crack potential indication. For producing WMA lower production temperatures are used and thus moisture susceptibility increases. Incomplete drying of aggregate causes moisture damage of mix as water remains confined in the aggregate skeleton.

II. PROPOSED METHODOLOGY

A. Selection and Laboratory Testing of Materials

Materials used in this research were having all the results with in the specified limit as per ASTM standards, and the aggregate gradation with nominal aggregate size of 19mm was used as per Marshall Mix Design.

Properties of asphalt mix are greatly influenced by gradation, surface texture and shape of the aggregates, as higher shear strength is provided by aggregates which are rough-textured and angular as compared to rounded shaped aggregate with smooth-textured and almost 95% of the mixture is composed of aggregate and remaining 5% is the asphalt binder, so aggregate is the component that provides resistance to deformation and provide a strong stone skeleton. According to the standard specifications of ASTM and BS for materials classification, compulsory tests were made on utilized aggregate and binder all the results were within the specified limits.

Asphalt content in RAP was determined using Ignition method in accordance with ASTM D 6307 – 98 and it was found that 4.46% of the total re-graded mass of RAP was aged-binder. While using Standard Test Method for Recovery of Asphalt from Solution by Abson method in accordance with ASTM D1856 – 09, to extract aged bitumen from RAP for testing. Table 2 and Table 3 shows the tests performed on bitumen.

The selected gradation is shown in Table 1 and Figure 1 shows gradation which is plotted with percentage passing verses sieve sizes.



Table -1 NHA Class-B Gradation Selected for Testing

| S. NO | Sieve Size (mm) | NHA Specification Range (% Passing) | Our Selection | Retained (%) |
|-------|-----------------|-------------------------------------|---------------|--------------|
| 1 | 19 | 100 | 100 | 0.00 |
| 2 | 12.5 | 75-90 | 82.5 | 17.50 |
| 3 | 9.5 | 60-80 | 70 | 12.50 |
| 4 | 4.75 | 40-60 | 50 | 20.00 |
| 5 | 2.38 | 20-40 | 30 | 20.00 |
| 6 | 1.18 | 5-15 | 10.00 | 20.00 |
| 7 | 0.075 | 3-8 | 5.5 | 4.50 |
| 8 | Pan | ... | ... | 5.50 |

Table -3 Weight of Aggregate as per Gradation

| Sieve Dia (mm) | % Passing | | | | | | |
|----------------|-------------------|-------------------|---------------|---------|---------|---------|---------|
| | NHA B Lower Limit | NHA B Upper Limit | Our Selection | 15% RAP | 25% RAP | 35% RAP | 50% RAP |
| 19 | 100 | 100 | 100 | 100 | 100 | 100 | 100 |
| 12.5 | 75 | 90 | 82.5 | 85.2 | 85.9 | 86.5 | 87.3 |
| 9.5 | 60 | 80 | 70.0 | 69.0 | 69.7 | 70.1 | 70.7 |
| 4.75 | 40 | 60 | 50.0 | 50.2 | 50.8 | 51.0 | 51.4 |
| 2.38 | 20 | 40 | 30.0 | 32.5 | 33.7 | 34.5 | 35.3 |
| 1.18 | 5 | 15 | 10.0 | 10.9 | 12.8 | 13.6 | 14 |
| 0.075 | 3 | 8 | 5.5 | 5.0 | 5.3 | 5.5 | 6.3 |

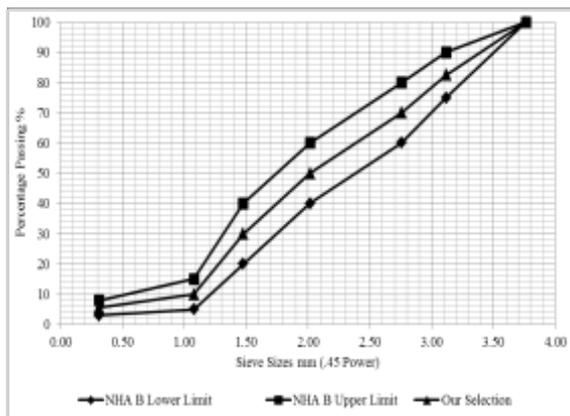


Fig. 1. Class-B Gradation plot with NHA Specified limit

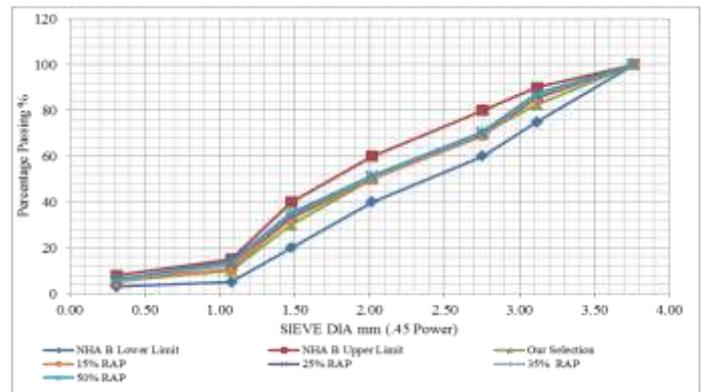


Fig. 2. Gradation plot of RAP Percentages with Specified limit of NHA Class B

The amount of RAP was varied by 0%, 15%, 25%, 35% and 50% in asphalt mix. Stability, flow values and volumetric were calculated using Marshall Mix design procedure. Therefore, five different RAP percentages and corresponding aggregate on different sieves were found which are shown in Table 2 and Table 3 while Figure 2 shows gradation which is plotted with percentage passing versus sieve sizes for mentioned percentages of RAP.

Table -2 RAP gradation

| Sieve Dia (mm) | RAP (% Retained) |
|----------------|------------------|
| 19 | 0.00% |
| 12.5 | 7.02% |
| 9.5 | 11.15% |
| 4.75 | 20% |
| 2.38 | 18% |
| 1.18 | 31% |
| 0.075 | 10.25% |
| Pan | 2.70% |

B. Preparation of Aggregates and Bitumen for Marshall Mix Design

After sieve analysis, aggregate were dried to constant weight at a temperature of 105^o to 110^o. The amount of aggregate needed for the preparation of marshall compacted specimen of 101.6 mm diameter, by Marshall Mix design method (ASTM D6926), should be approximately 1200 g. As there were five types of gradations with respect to percentage of RAP i.e. 0%, 15%, 25%, 35%, and 50%. Specimens were prepared at five different binder contents of 3.5, 4.0, 4.5, 5.0 and 5.5%. The amount of asphalt cement added to each specimen was taken as the percentage of total weight of the mix. The reason of five trial blend was to select a mix that performs optimal at minimum bitumen content at 4% air voids. The volumetric properties, stability and flow were measured and verified in light of Marshall Mix design criterion by revising the Marshall Mix design procedure thrice for each mix, thus fifteen specimens for each mentioned percentage of RAP were prepared for OBC determination and thus a total of 75 specimens were prepared for determination of five OBCs, based on varying percentage of RAP. Separate graphical plots

for all values were drawn as tabulated in Table 4 and shown in Figure 3 (a, b, c, d, e, and f).

Table -4 Volumetric for Different Percentages of RAP

| (%) RAP | OBC at 4% Air Voids | VMA, (%) | VFA, (%) | Stability, (KN) | Flow, (mm) | Unit Weight, (mg/cm ³) |
|---------|---------------------|----------|----------|-----------------|------------|------------------------------------|
| 0 | 4.31 | 13.49 | 70.04 | 12.32 | 2.72 | 2.37 |
| 15 | 4.33 | 13.56 | 70.19 | 12.37 | 2.75 | 2.37 |
| 25 | 4.39 | 13.96 | 71.10 | 13.02 | 2.93 | 2.36 |
| 35 | 4.5 | 13.66 | 70.7 | 13.12 | 2.89 | 2.37 |
| 50 | 4.59 | 13.79 | 71.07 | 13.22 | 2.87 | 2.37 |



Fig. 4. Sasobit Prills

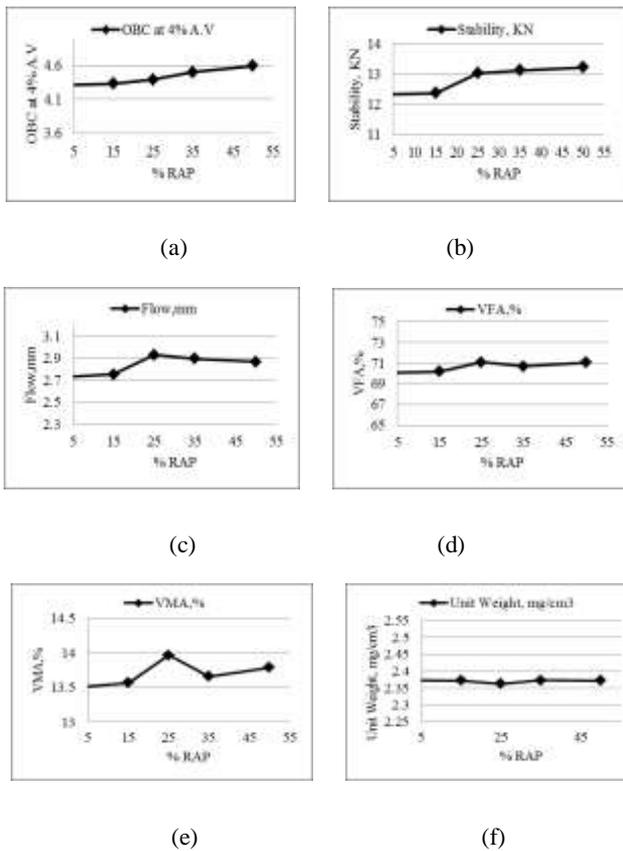


Fig. 3. (a, b, c, d, e & f): Plots between RAP percentages Vs Volumetric

C. Sample Preparation for Performance Tests

Sasobit utilized in the study was in the form of prills as shown in Figure 4, and was imported through an authorized product distributor. In this study Sasobit was pre-blended with the binder in appropriate amount; samples were prepared with 0%, 1%, 2% and 3% Sasobit of OBC. Thus based on five percentages of RAP and with further addition of Sasobit percentages to each of the RAP percentage there were total of twenty mixes.

Superpave mix design procedure was used to prepare specimens for performance testing. After sieving, similar to marshal mix design, the aggregates were dried to constant weight at a temperature of 105°C to 110°C. Mixing temperature of 160±5°C and compaction temperature of 135°C was used for HMA, while using 125±5°C and 100°C as mixing and compaction temperature for WMA respectively, as obtained from the viscosity plots of binders through RV test at 135oC and 160oC and also the general manufacturing temperature range for WMA is 93°C to 135°C. The required quantity of aggregate for preparing 152.4 mm diameter gyratory compacted specimens was 5000 g. Before compaction, conditioning of loose mix for short term aging was carried out for 2 hours at compaction temperature. Compaction of specimens was done by providing 125 gyrations as specified by the Superpave mix design. Further, resizing of samples for testing were carried out by utilizing saw cutter and core cutter, to obtain standard sample of 38.1 mm height and 152.4 mm diameter for wheel tracker test and 63±2.5 mm height and 101.6 mm diameter for moisture damage testing through UTM as shown in Figure 5 and 6 respectively.



Fig. 5. HWT Tested Sample



Fig. 6. UTM Tested Sample

Table -5 HWTD & ITS Tests Results

| Specification | Codes | Average RUT Depth (mm) | S1, (kPa) | S2, (kPa) | TSR= S2/S1 |
|---------------------|-------|------------------------|-----------|-----------|------------|
| 0% RAP, 0% SASOBIT | R0S0 | 4.455 | 777.85 | 777.5 | 99.96 |
| 0% RAP, 1% SASOBIT | R0S1 | 4.410 | 779.35 | 777.35 | 99.74 |
| 0% RAP, 2% SASOBIT | R0S2 | 4.383 | 780.2 | 776.3 | 99.50 |
| 0% RAP, 3% SASOBIT | R0S3 | 4.420 | 781.3 | 774.15 | 99.08 |
| 15% RAP, 0% SASOBIT | R15S0 | 3.690 | 783.05 | 770.55 | 98.40 |
| 15% RAP, 1% SASOBIT | R15S1 | 3.545 | 785.15 | 768.7 | 97.90 |
| 15% RAP, 2% SASOBIT | R15S2 | 2.855 | 787.9 | 767.2 | 97.37 |
| 15% RAP, 3% SASOBIT | R15S3 | 2.965 | 789.25 | 766.45 | 97.11 |
| 25% RAP, 0% SASOBIT | R25S0 | 2.820 | 791.8 | 764.7 | 96.58 |
| 25% RAP, 1% SASOBIT | R25S1 | 2.680 | 794.15 | 763.65 | 96.16 |
| 25% RAP, 2% SASOBIT | R25S2 | 2.615 | 796.75 | 763.3 | 95.80 |
| 25% RAP, 3% SASOBIT | R25S3 | 2.405 | 802.45 | 761.7 | 94.92 |
| 35% RAP, 0% SASOBIT | R35S0 | 2.130 | 806.85 | 759.1 | 94.08 |
| 35% RAP, 1% SASOBIT | R35S1 | 1.940 | 817.2 | 757.35 | 92.68 |
| 35% RAP, 2% SASOBIT | R35S2 | 1.845 | 820.75 | 748.4 | 91.18 |
| 35% RAP, 3% SASOBIT | R35S3 | 1.655 | 828.2 | 739.15 | 89.25 |
| 50% RAP, 0% SASOBIT | R50S0 | 1.530 | 835.1 | 730.85 | 87.52 |
| 50% RAP, 1% SASOBIT | R50S1 | 1.410 | 842.3 | 715.6 | 84.96 |
| 50% RAP, 2% SASOBIT | R50S2 | 1.060 | 858.7 | 710.3 | 82.72 |
| 50% RAP, 3% SASOBIT | R50S3 | 0.850 | 877.6 | 692.45 | 78.90 |

S1 = Average Strength of Un- Conditioned samples,
S2 = Average Strength of Conditioned samples

D. Permanent Deformation (Wheel Tracker Tests Results)

Wheel tracker tests were conducted on specimens prepared for rutting under wet condition. For wheel tracker test a total of sixty samples were prepared for the twenty mixes. All the controlled specimens showed good resistance to rutting, whereas the specimens with 0% and 15% RAP shows higher resistance to rutting at 2% Sasobit addition and at 3% percent Sasobit addition these samples have less rut resistance than that of samples having 2% Sasobit. But samples with higher percentages of RAP that is 25%, 35% and 50% showed higher rut resistance at 3% Sasobit. All of the specimens passed the wheel tracker test criteria of 12.5 mm rut depth at a temperature of 45oC, which is the required testing temperature for bitumen of 58 grades (ARL 60/70) used in the study, while the numbers of passes were fixed to ten thousand which is the required criteria for rutting. The wheel tracker tests results are shown in Figure 7 and tabulated in Table 5.

E. Moisture Damage (ITS Test Results)

Moisture susceptibility testing were carried out on asphalt mixtures according to ALDOT. For the twenty different mixes a total of 120 gyratory samples at 4% air voids were prepared and tested for Indirect Tensile Strength. Thus six samples per mix were prepared, three of them were tested unconditioned by only placing in a water bath at a temperature of 25°C for one hour right before testing, while the other three specimens per mix were soaked in warm water at a temperature of 60oC for 24 hours, followed by placing in a water bath at 25oC for one hour before being tested for Indirect Tensile Strength. The raw wet (conditioned) and dry (unconditioned) strength values for the 20 mixtures are shown in Figure 8 while the tensile strength ratios are shown in Figure 9. From the results it is clear that as we increase the RAP percentage the strength of the asphalt mix increases.

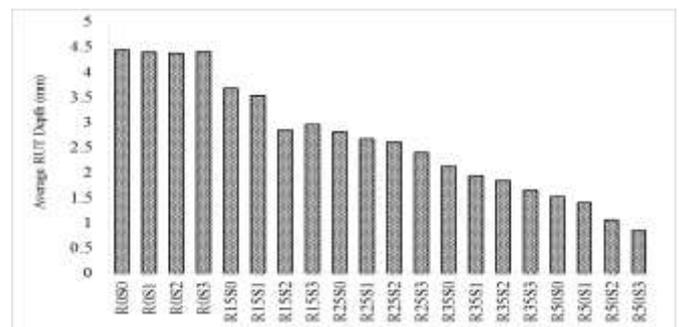


Fig. 7. Average Rut depth from HWTD testing

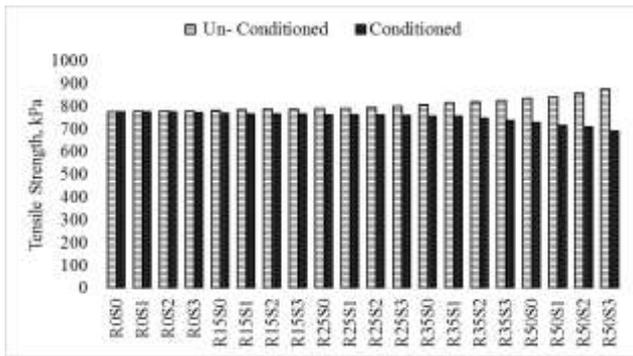


Fig. 8. Tensile Strength of different mixes

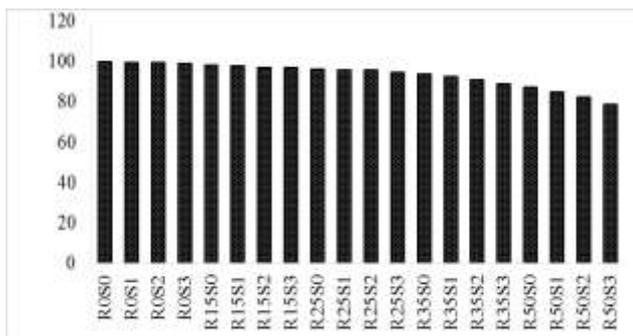


Fig 9: Average TSR for different mixes

The minimum tensile strength ratio specified by superpave for mixes having no anti-stripping agent is 80%. The calculated tensile strength ratios for the 20 mixes were all above 80 percent, except for the mix having 3% Sasobit and 50% RAP which was 78.9%. Also, the indirect tensile strength values show that all the conditioned samples give strength value lower than that of unconditioned samples, showing that, Sasobit increases the moisture susceptibility of asphalt mixes.

Figure 10 shows Gyrotary Samples Before and After Testing.



Fig. 10. Gyrotary Samples Before and After Tests

III. CONCLUSIONS

The conclusions drawn from laboratory tests are listed as under;

Resistance of HMA to rutting containing RAP increases by increasing RAP content.

Rut resistance of controlled asphalt mixes and asphalt mixes containing RAP increases by increasing Sasobit content as compared to controlled mixes and mixes containing RAP only.

Increase in rut resistance is also due to decreased production temperature and this may be associated more to the reduced binder aging.

Asphalt mixes having low percentages of RAP i.e. up to 15% give best rut resistance at 2% sasobit addition and then decreases unlike for mixes with higher percentages of RAP i.e. above 15% for which rut resistance increases linearly up to 3% sasobit. The decreased in rut resistance may be due to increased workability and viscosity.

The indirect tensile strength for mixes with either sasobit alone or both sasobit and RAP were slightly higher as compared to the control mixes. Which may be due to the formation of lattice structure.

The indirect tensile strength for mixes with sasobit plus RAP was slightly higher, as compared to mix containing RAP only.

The resistance against moisture damage of asphalt mixes containing RAP or sasobit or both is lower than that of control mixes, and this may be contributed to lower mixing and compaction temperatures for WMA as compared to HMA and potential for moisture damage increases due to incomplete drying of aggregate in the resultant asphalt mix using WMA technology. The moisture damage may be due to water trapped in the coated aggregate.

For asphalt mixes with 0% RAP the tensile strength ratios are very slightly lower from that of control mix i.e. 99.96% for control mix and 99.74%, 99.5%, and 99.08% for addition of 1%, 2% and 3% sasobit respectively.

For any percentage of RAP and sasobit the values of tensile strength ratio are above the minimum range of 80% except for 50% RAP and 3% sasobit which is 78.90%. While for the mix with 3% sasobit and 35% RAP the tensile strength ratio is 82.72% which is too close to the lower limit.

As far as rutting resistance and moisture susceptibility is concerned which are the most prevalent forms of asphalt concrete distresses in our region and also in most of developing countries with no control on wheel axel loads the recommended percentages are 3% sasobit and 30-40% RAP for adequate resistance to rutting and moisture damage. Further it is recommended that it's a better option to use 2% sasobit with control mixes and mixes containing lower percentages of RAP i.e. up to 15%, while for higher percentages of RAP better option is to use 3% sasobit.



Conflict of Interest Statement

The authors of this research paper, whose names are listed on title page, certify that they have conducted this research as a part of project financially supported by Pakistan Higher Education Commission with the title Characterization of Reclaimed Asphalt Pavement (RAP) for use in pavement construction industry in Pakistan.

Acknowledgement and Disclaimer

The researchers appreciatively recognize the support of Pakistan Higher Education Commission for sponsoring this research project under National Research Program for Universities (NRPU) with award No.20-45%/R&D/HEC/14/1067. This is only a technical article for experimental investigation along with optimization of RAP and sasobit for permanent deformation and moisture damage of asphalt mixes the mixtures' durability (moisture susceptibility) was measured by the Universal Testing Machine (UTM) performing Indirect Tensile Strength (ITS) test and permanent deformation (Rutting) by Hamburg Wheel Tracking device (HWTD). This research study does not establish a standard, specification, or a regulation.

IV. REFERENCES

- [1] Al-Qadi I.L., Aurangzeb Q. and Carpenter, S.H., (2012), "Impact of High RAP Content on Structural and performance Properties of Asphalt Mixtures", Research Report FHWA-ICT-12-002, Illinois Center for Transportation.
- [2] Hurley, G.C. and Prowell, B. D. (2006b) "Evaluation of Evotherm for Use in Warm Mix Asphalt," Report NCAT 06-02, National Center for Asphalt Technology, Auburn University, Auburn, Alabama.
- [3] Abraham, E. (2014). Effects of Aggregate and Mixture Properties on the Rutting Performance of HMA Wearing Course (A Case Study on the Gohatsion-Dejen Trunk Road Segment) (Doctoral dissertation, AAU).
- [4] Hurley, G. C., & Prowell, B. D. (2005). Evaluation of Aspha-Min zeolite for use in warm mix asphalt. NCAT report, 5(04).
- [5] MAHA, I., SUBAGIO, B. S., EFFENDHI, F., & RAHMAN, H. (2015). Performance of Warm Mix Asphalt Concrete Binder Course (AC-BC) With Reclaimed Asphalt Pavement. *Journal of the Eastern Asia Society for Transportation Studies*, 11(0), 1745-1753.
- [6] McCormack, S. M., Sturgill, R. E., Howell, B., Van Dyke, C. W., & Kreis, D. (2014). Green Infrastructure.
- [7] Rossi, D., Filippi, S., Merusi, F., Giuliani, F., & Polacco, G. (2013). Internal structure of bitumen/polymer/wax ternary mixtures for warm mix asphalts. *Journal of Applied Polymer Science*, 129(6), 3341-3354.
- [8] Liu, J., & Li, P. (2011). Low temperature performance of sasobit-modified warm-mix asphalt. *Journal of Materials in Civil Engineering*, 24(1), 57-63.
- [9] Capitão, S. D., Picado-Santos, L. G., & Martinho, F. (2012). Pavement engineering materials: Review on the use of warm-mix asphalt. *Construction and Building Materials*, 36, 1016-1024.
- [10] Chowdhury, A., & Button, J. W. (2008). A review of warm mix asphalt (No. SWUTC/08/473700-00080-1). Texas Transportation Institute, the Texas A & M University System.
- [11] Ahmed, T. A. H. (2014). Investigating the rutting and moisture sensitivity of warm mix asphalt with varying contents of recycled asphalt pavement.
- [12] Hussain, S. (2012). Determining the Contribution of Different Structural Layers of Asphalt Pavement to Rutting using Transverse Profile Analysis. MS Thesis, National University of Sciences and Technology, Pakistan.
- [13] Mogawer, W., Austerman, A., Kluttz, R., & Roussel, M. (2012). High-Performance Thin-Lift Overlays with High Reclaimed Asphalt Pavement Content and Warm-Mix Asphalt Technology: Performance and Workability Characteristics. *Transportation Research Record: Journal of the Transportation Research Board*, (2293), 18-28.
- [14] O'Sullivan, K. A. (2009). The effects of warm mix asphalt additives on recycled asphalt pavement (Doctoral dissertation, WORCESTER POLYTECHNIC INSTITUTE).
- [15] Zhao, S., Huang, B., Shu, X., & Woods, M. (2013). Comparative evaluation of warm mix asphalt containing high percentages of reclaimed asphalt pavement. *Construction and Building Materials*, 44, 92-100.
- [16] Washington State Department of Transportation. (2009). 5.6 HMA Mix Design - Testing. Retrieved January 2009, from PTC Training Guides: http://training.ce.washington.edu/WSDOT/Modules/05_m ix_design/05-6_body.htm