



# IJEAST

INTERNATIONAL JOURNAL  
OF ENGINEERING APPLIED SCIENCE  
AND TECHNOLOGY



**VOLUME : 4    ISSUE : 04    Print / Issue Publication Date: 03-Oct-2019**



**ISSN : 2455-2143**



**DOI : 10.33564/IJEAST.2019.v04i04.061**

Indexed In



[WWW.IJEAST.COM](http://WWW.IJEAST.COM)

[editor@ijeast.com](mailto:editor@ijeast.com)



# AN EXPERIMENTAL STUDY ON THE PERFORMANCE OF MARINE CLAY SUBGRADE TREATED WITH SAWDUST AND LIME

Shaik Ishaq Ahmed  
Post Graduate Student,  
Dept. of Civil Engineering,  
UCEK, JNTUK  
Kakinada, A.P., India

Dr. K Purnanandam  
Professor,  
Dept. of Civil Engineering,  
UCEK, JNTUK  
Kakinada, A.P., India

**Abstract:** *Roads are the arteries through which Indian economy grows. India is a country which is having a coastal line of 7516.6 km. This coastal region mostly consists of marine clay deposits. For the construction of roads, using of locally available materials and soils will be economical. But in coastal region using marine clay (locally available) as a subgrade will not yield desirable results due to its poor engineering properties. Replacing soil is not economically feasible as it increases the budget of the project. Stabilization of the existing soil is a possible solution in such cases. Lime is a commonly available chemical and sawdust is a waste product from wood and timber industry. The study of using the above materials for the stabilization of marine clay is discussed here.*

**Keywords:** *Marine Clay, Sawdust, Lime, MDD, OMC, CBR.*

## I. INTRODUCTION

In the construction of pavements, subgrade plays a pivotal role. Subgrade performance will affect the lifespan of the pavement. An appropriate soil has to be selected which can be used as a subgrade. Poor performance of subgrade leads to high construction costs. To resolve this problem, different methods have been developed to minimize the variability in subgrade characteristics. Marine clay is one of the problematic soils which can be found on coastal region. Marine clays are microcrystalline in nature and it has clay minerals like illite, chlorite and kaolinite. Marine clays tend to become stiff when dried but becomes soft when wet. High shrinkage and low shear strength are the properties of marine clay. Due to its poor properties, marine clay has to be pre-treated to be used as a subgrade in highways. In improving soft soil, generally replacement of soft soil with stronger material is to be used. Replacement of soil increases cost of the

project. It was found that the utilization of the industrial wastes like sawdust is an alternative to stabilize the soil for various construction purposes. When an activator like lime is added to the sawdust, the results are very encouraging.

In the present study, sawdust and lime are added to marine clay to evaluate its performances through laboratory tests such as the standard proctor test and California bearing ratio test.

## II. REVIEW OF LITERATURE

- Hydel et al (1993) presented the engineering properties of marine clay under cyclic loading.
- The influence of marine clay treated with air cooled slag with additives like calcium chlorite to improve the engineering properties was studied by Prasad Raju GVR et al., (2001).
- Chu, J et al (2002) reported that consolidation and permeability properties of Singapore marine clay based on laboratory and field investigations.
- GVR Prasad Raju et al., (2016) reported that Marine Clay when treated with various percentages of quarry dust as an admixture and Ferric chloride as an additive, the deformation and load carrying capacity of treated marine clay increased greatly.

## III. OBJECTIVES OF THE STUDY

The objectives of the present experimental study are as follows:

- To determine properties of marine clay.
- To evaluate the performance of marine clay when stabilized with sawdust as an admixture.



- To determine suitability and performance of marine clay when stabilized with optimum of sawdust and lime when it is used as subgrade.

#### IV. MATERIALS USED

##### A. Marine clay

Marine clay sample was collected from a dredging site, where dredging was carried out at a depth of 2.5 m below the sea level near Kakinada SeaPorts Ltd. The collected samples were black in color. The presence of sea shells indicated the presence of organic content. The hydrometer analysis conducted on marine clay shows 57.40% of clay and 25.40% of silt.

S. No	Properties	Untreated Marine Clay	
1	Soil classification	Gravel (%)	0
		Sand (%)	17
		Silt (%)	25.60
		Clay (%)	57.40
2	Liquid limit (%)	73.67	
3	Plastic limit (%)	26.40	
4	Plasticity index (%)	47.27	
5	Shrinkage limit (%)	11.87	
6	Soil classification	CH	
7	Specific gravity	2.342	
8	Differential free swell (%)	90	
9	MDD(g/cc)	1.324	
10	OMC (%)	34.48	
11	CBR (%)	1.137	
12	cohesion(kN/m <sup>2</sup> )	90	
13	Angle of internal friction	3.12 <sup>0</sup>	

##### B. Sawdust

- Sawdust is a waste from the wood and timber industry. It is the residue generated by sawteeth when wood is cut into lumber.
- As it possesses a firing capacity, it is normally used as a fuel source in thermal

processes (biomass). It is also used as insulating material.

- Sawdust is the residue generated by sawteeth when wood is cut into lumber.

##### C. Lime

Lime chemically known as Calcium oxide (CaO), commonly known as quick lime is a widely used chemical.

##### Physical Properties of Lime:

- Lime is a white amorphous solid.
- It has a high melting point of 2600<sup>0</sup>
- It is highly stable and even fusion cannot decompose it.

Table 2: Physical Composition of Sawdust

Property	size (in mm)	Value
Particle Size Distribution	4.75	100
	2.0	95
	0.6	81
	0.425	48
	0.21	30
	0.075	9
Specific Gravity		2.05

Table 3 : Chemical Composition of Lime

S.No	Components	Component %
1	Assay	95
2	Chloride	0.01
3	Sulphate	0.2
4	Arsenic	0.0004
5	Lead	0.001
6	Insoluble Matter	1

Courtesy: [www.sciencedirect.com](http://www.sciencedirect.com)



**V. LABORATORY STUDIES**

The laboratory studies were carried out on the samples of marine clay, marine clay treated with optimum of sawdust, marine clay treated with optimum of sawdust and lime.

**Atterberg limits:**

The liquid limit, plastic limit and thereby the plasticity index were determined using Casagrande's liquid limit apparatus as per the procedures laid down in IS: 2720 part 4 (1970) on marine clay; marine clay+15% sawdust; Marine clay+ 15% sawdust + 4% lime.

**Differential free swell index:**

This test is performed by pouring slowly 10 gm of dry soil, 10 gm of (soil+ lime), 10 gm of (soil + lime + sawdust) passing through 425 micron sieve, in two different 100 cc glass jars filled with distilled water and other with kerosene . The swollen volume of Marine Clay; Marine Clay-Lime; Marine clay-Lime -Sawdust mixes are recorded.

$$\text{Differential Free Swell Index} = \frac{(V_d - V_k)}{V_k} * 100$$

$V_d$ = Volume of soil in distilled water after 24 hours.

$V_k$  = volume of soil in kerosene after 24 hours.

**Specific Gravity Test:**

Specific gravity is the ratio of the mass of unit volume of soil at a stated temperature to the mass of the same volume of gas free distilled water at a stated temperature. The specific gravity of a soil is used in the phase relationship of air, water, and solids in a given volume of the soil. Specific gravity test was carried out by Pycnometer as per IS 2720 Part 3 (1980).

**Modified Proctor compaction Test:**

The optimum moisture content and maximum dry density have an important role in changing the strength properties of clay. Preparation of soil sample for proctor's compaction test was done as per IS: 2720 part-6 (1974).

**California Bearing Ratio Test:**

The California bearing ratio tests are conducted on Marine Clay, Marine Clay treated with sawdust, and Marine clay with optimum of sawdust and percentage variation of lime as per IS 2720 part 16 (1979), subjected to an Optimum moisture content obtained from Compaction test. The samples soaked for a curing period of 4 days. The test was

conducted under a constant strain rate of 1.25mm/min. The proving ring reading is noted for 50 divisions, and loading was continued until 3 or more readings were either decreasing or constant.

**VI. RESULTS AND DISCUSSION**

*Compaction and CBR values of marine clay treated with various percentages of lime*

**(a) Compaction Test Results :**

Marine clay was replaced by sawdust in different percentages varying from 5% to 25% to improve its properties. Upon performing modified proctor compaction test, an optimum of 15% sawdust was obtained in this case. Thereafter Marine clay with 15 % sawdust was treated with lime of percentage variations of 3% to %7. Finally an optimum of 4% lime was obtained. Tables 4,5 and figures 1, 2 and 3 present the OMC and MDD values of various mix proportions of marine clay.

Table 4: MDD Values for Various Mix Proportions of Marine Clay and Sawdust

S.No	MARINE CLAY %	SAWDUST %	MDD g/cc
1	100	0	1.324
2	95	5	1.262
3	90	10	1.284
4	85	15	1.361
5	80	20	1.204
6	75	25	1.193

Table 5: MDD Values for Various Mix Proportions of Marine Clay, Sawdust and Lime

S.No	MARINE CLAY %	SAWDUST %	LIME %	MDD g/cc
1	82	15	3	1.304
2	81	15	4	1.318
3	80	15	5	1.296
4	79	15	6	1.228
5	78	15	7	1.168

Table 6: CBR Values of Marine Clay Treated with various percentages of Sawdust



S.No	Marine Clay %	Sawdust %	Soaked C.B.R
1	95	5	1.120
2	90	10	2.017
3	85	15	4.258
4	80	20	0.896
5	75	25	0.672

	(%)				
8	CBR (%)		1.137	4.258	8.843
9	Cohesion (kN/m <sup>2</sup> )	C	90	74	55
10	Angle of internal friction	Φ	3.12 <sup>0</sup>	6 <sup>0</sup>	10 <sup>0</sup>

Table 7: CBR Values of Marine Clay Treated with Various Percentages of Sawdust and Lime

S.No	MARINE CLAY %	SAW DUST %	LIME %	SOAKED C.B.R
1	82	15	3	2.017
2	81	15	4	8.843
3	80	15	5	3.585
4	79	15	6	2.465
5	78	15	7	1.793

Table 8: Laboratory Test Results Of The Untreated And Treated Marine Clay

S.No	Properties	Symbol	Marine clay	Marine clay +15% sawdust	Marine clay+15% sawdust+4% lime
1	Liquid limit (%)	W <sub>l</sub>	73.67	62.81	51.93
2	Plastic limit (%)	W <sub>p</sub>	26.40	28.34	30.09
3	Plasticity index (%)	I <sub>p</sub>	47.27	34.47	21.84
4	Specific gravity	G	2.342	2.563	2.603
5	Differential free swell index (%)	D <sub>f</sub>	90	35	24
6	MDD(g/cc)	Y <sub>d</sub>	1.324	1.361	1.318
7	OMC	W	34.48	30.02	28.69

VII. GRAPHS

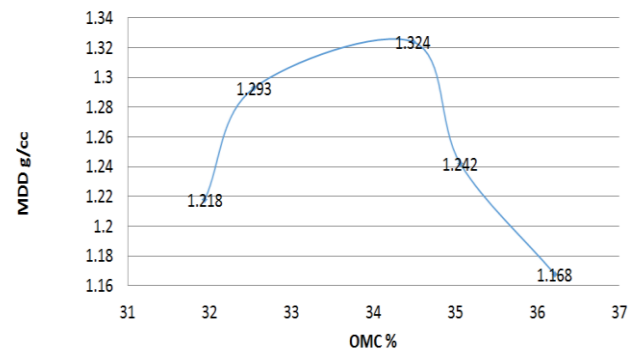


Fig.1 OMC and MDD Values of Untreated Marine Clay

COMPACTION GRAPHS AT A GLANCE

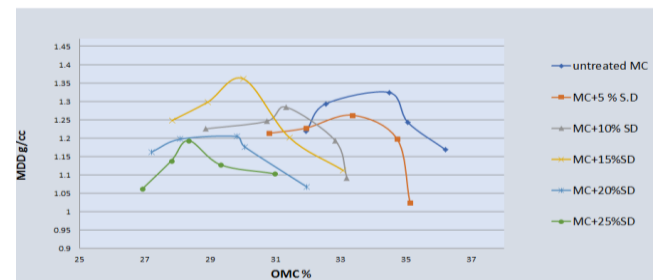


Fig.2 OMC and MDD values of treated marine clay treated with various percentages of sawdust

COMPACTION GRAPHS AT A GLANCE

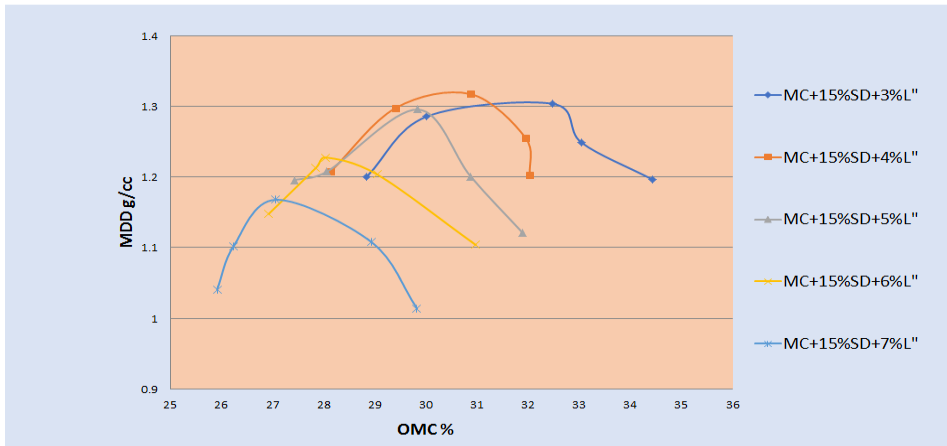


Fig.3 OMC and MDD plots of treated marine clay treated with various percentages of sawdust and lime

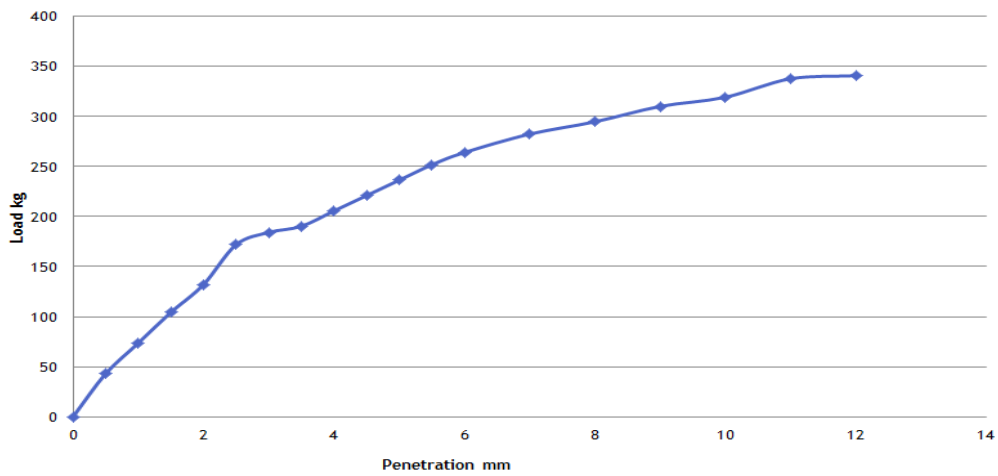


Fig.4 CBR graph of untreated marine clay

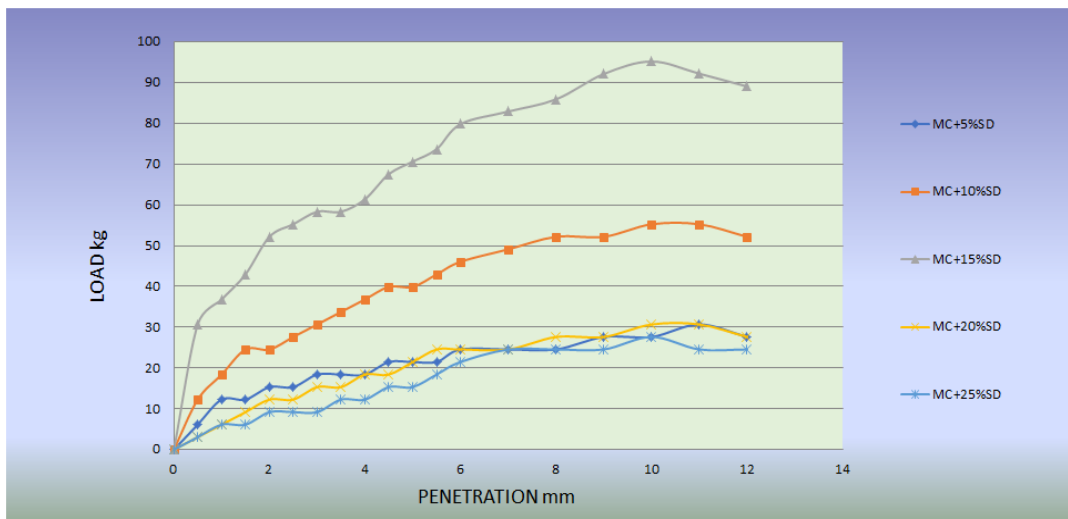


Fig.5 CBR graphs of treated marine clay with various percentages of sawdust

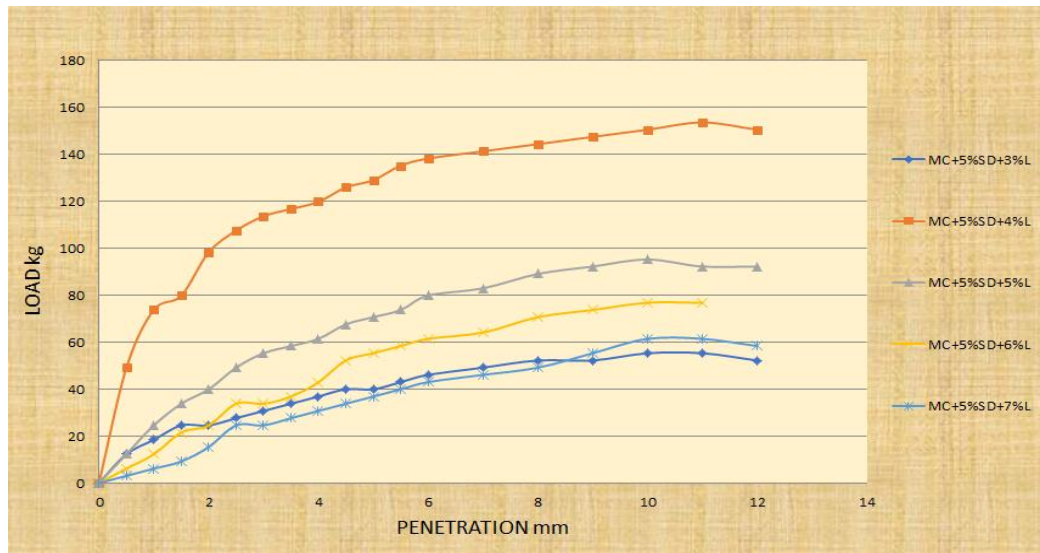


Fig.6 CBR graphs of treated marine clay with various percentages of sawdust and lime

### VIII. CONCLUSIONS

**Upon addition of 15 % saw dust the following conclusions are made on the marine clay tested:**

- The liquid limit has been decreased by 14.74%.
- The plastic limit has been increased by 7.34%.
- The plasticity index has been diminished by 27.50%.
- The shrinkage limit was raised by 25.69%.
- Specific gravity was increased by 8.81%.
- DFS got lowered by 61.11%.
- Maximum dry density was increased by 2.79 %.
- CBR value went up by 274.49 %.

**On addition of 4% Lime and 15% saw dust to marine clay the following observations are made:**

- The liquid limit has been decreased by 29.50%.
- The plastic limit has been increased by 13.97%.
- The plasticity index has been diminished by 53.79%.
- The shrinkage limit was raised by 46.08%.
- Specific gravity was increased by 20.54%.
- DFS got lowered by 73.33%.
- Maximum dry density was reduced by a margin of 0.45 %.
- CBR value went up by 589.79 %.

### IX. ACKNOWLEDGEMENT

I would like to express my deep sense of gratitude towards my guide Dr. K Purnanandam, Dept. of Civil Engineering, UCEK, JNTUK, Kakinada for his huge support in my project and also in the publication of this paper. I also thank my other faculty members of Soil Mechanics and Foundation Engineering, lab technicians of Soil Mechanics Laboratory, Dept. of Civil Engineering, UCEK, JNTUK for extending their support by all means. I also wholeheartedly thank my classmates of SMFE, Dept. of Civil Engineering, UCEK, JNTUK for lending their help when needed.

### X. REFERENCES

1. Teresa Sunny and Annie Joy (2016), "Study on the Effects of Marine Clay Stabilized with Banana Fibre", *International Journal of Scientific Engineering and Research (IJSER)*, Volume- 4 Issue 3, pp.96-98 .
2. Prasada Raju GVR, P. Sowmya Ratna, DSV Prasad, (2016), "Performance of Recron-3s Fibre with Lime in Expansive Soil Stabilization", *IOSR Journal of Mechanical and Civil Engineering (IOSR-JMCE)*, Volume 13, Issue 6, Pp. 74-79.
3. Prasad DSV, H Venkateswarlu, N Janardhan Rao, J Chaitanya Kumar (2015) "Strength Behaviour of Marine Clay Treated with Rice Husk Ash", *International Journal of Engineering Sciences & Research Technology*, ISSN: 2277-9655, PP 561-567.
4. Dayakar Babu et al (2013) "Strength Behaviour of Marine Clay Stabilized with Lime – Quarry Rock Dust and Waste Plastics" *Proceeding of Conference Paper June 2013.*



5. Koteswara Rao.D, G.V.V. Rameswara Rao, P.R.T. Pranav (2012) “A Laboratory Study on the Effect of Rice Husk Ash & Lime on the Properties of Marine Clay” International Journal of Engineering and Innovative Technology (IJEIT), Volume 2, Issue 1, PP 345-353.
6. Rajasekaran, G and Narasimha Rao, S (2002), Compressibility Behaviour of Lime Treated Marine Clay, Journal of Ocean Engineering, volume-29, pp. 545-559.
7. IS : 2720 Part - 3 (1980) : Determination of Specific Gravity .
8. IS : 2720 Part - 4 (1975) : Grain size analysis.
9. IS : 2720 Part - 5 (1970) : Determination of Liquid Limit and Plastic Limit
10. IS : 2720 Part - 6 (1972) : Determination of Shrinkage Limit .
11. IS : 2720 Part - 6 ( 1974) : Determination of Dry Density and Optimum Moisture Content .
12. IS : 2720 Part -16 ( 1979) : Determination of California Bearing Ratio .

# IJEAST

INTERNATIONAL JOURNAL  
OF ENGINEERING APPLIED SCIENCE  
AND TECHNOLOGY

## ABOUT IJEAST

International Journal of Engineering Applied Science and Technology (IJEAST) is a peer-reviewed, open access journal that publishes high-quality research papers in the field of Engineering, Applied Science and Technology.

IJEAST aims to provide a platform for researchers, academicians, and professionals to share their innovative ideas, research findings, and practical experiences with the global scientific community.

## FOCUS AREAS

- Engineering
- Applied Science
- Technology
- Innovation & Development
- Interdisciplinary Studies



### PEER REVIEWED

All submissions are rigorously peer reviewed to ensure quality.



### OPEN ACCESS

Free and unrestricted access to research for all.



### GLOBAL REACH

Connecting researchers and professionals worldwide.



### TIMELY PUBLICATION

We ensure a swift and efficient publication process.



For more information, visit our website

[www.ijeast.com](http://www.ijeast.com)



INTERNATIONAL JOURNAL  
OF ENGINEERING APPLIED SCIENCE  
AND TECHNOLOGY

✉ [editor@ijeast.com](mailto:editor@ijeast.com)

🌐 [www.ijeast.com](http://www.ijeast.com)

📍 India



2455-2143